

Finite temperature superfluid density in very underdoped cuprates

Igor F. Herbut and Matthew J. Case

Department of Physics, Simon Fraser University, Burnaby, British Columbia, Canada V5A 1S6

The combination of a large gap, low transition temperature, and quasi two-dimensionality in strongly underdoped high temperature superconductors severely constrains the behavior of the *ab*-plane superfluid density ρ with temperature T . In particular, we argue that the contribution of nodal quasiparticles to $\rho(T)$ is essential to account both for the amplitude of, and the recently observed deviations from, the Uemura scaling. A relation between T_c and $\rho(0)$ which combines the effects of quasiparticle excitations at low temperatures and of vortex fluctuations near critical temperature is proposed and discussed in light of recent experiments.

High temperature superconductors appear most strikingly different from those of standard BCS variety when underdoped. While the observed gap in the single-particle density of states is large and appears to be only increasing with underdoping [1], the *ab*-plane superfluid density at $T = 0$, $\rho(0)$, at the same time is small and known to be continuously decreasing [2]. The superconducting transition temperature T_c appears to scale approximately linearly with $\rho(0)$, and this simple relation between the two fundamental quantities has been ubiquitous in cuprates and widely known as the Uemura scaling [2]. Recently, new measurements of the penetration depth in the strongly underdoped $YBa_2Cu_3O_{7-\delta}$ (YBCO) suggested a significant deviation from the Uemura relation [3], [4]. In this note we point out that the combination of three characteristics of underdoped cuprates, namely quasi two-dimensionality, a large superconducting gap, and low T_c , irrespective of what the microscopic mechanism behind the latter two may be, severely constrains the form of $\rho(T)$. In particular, we argue that even the early data of [2] are difficult to explain quantitatively by the phase fluctuations alone, and that the quasiparticle contribution should make the curve $T_c(\rho(0))$ *convex*, as we believe better describes what is being experimentally observed [3], [4], [5].

We begin from the early data on T_c vs. $\rho(0)$ [2], [6] by extracting a quasi-universal number that characterizes this relationship [6]. The helicity modulus in a two-dimensional (2D) superfluid layer may be expressed in units of Kelvin when written as

$$\rho(T) = \frac{\hbar^2 d |\Psi_0|^2}{k_B m^*}, \quad (1)$$

where $|\Psi_0|^2 = m^* c^2 / 16 \pi e^2 \lambda(T)^2$ is the superfluid density, d a layer thickness, and $\lambda(T)$ the in-plane penetration depth. Inserting all the requisite constants one finds

$$\rho(T) = 6.2 K \frac{d/10 \text{\AA}}{(\lambda(T)/\mu\text{m})^2}. \quad (2)$$

In the case of layered quasi two-dimensional materials like cuprates there is some ambiguity in defining the length d . Assuming it is the minimal thickness along the *c*-axis so that the material still superconducts, d may be estimated from the measurements on superconductor-insulator superlattices [7] or from the crossing-point phenomenon in

magnetization measurements [6]. Using $10 \text{\AA} < d < 12 \text{\AA}$, with the lower boundary corresponding to the measurement of Goodrich et al. [8] on superlattices and the upper to the thickness of one *c*-axis unit cell in YBCO, together with $T_c = (3.2 \pm 0.2)(\mu\text{m})^2 \text{K} / \lambda^2(0)$ [2], [6], one finds that

$$\frac{\rho(0)}{T_c} = Q, \quad (3)$$

with the dimensionless amplitude $1.82 < Q < 2.48$ in YBCO. Similarly, using $d = 7.6 \text{\AA}$ [6] and $T_c = (3.0 \pm 0.5)(\mu\text{m})^2 \text{K} / \lambda^2(0)$ [6], [9] one finds $1.37 < Q < 1.88$ in $La_{2-x}Sr_xCuO_4$ (LSCO). Evidently, the amplitude Q is not truly universal, but it is a pure number and most likely around *two*.

First, we argue that assuming that phase fluctuations alone reduce the superfluid density in underdoped cuprates [10], [11] leads to difficulties in accounting for the observed value of Q . Consider an anisotropic quantum XY model describing thermal and quantum fluctuations of the phase of the order parameter,

$$\begin{aligned} S = & -J \int_0^\beta d\tau \sum_{\vec{x}, \hat{r}, z} \cos(\theta(\vec{x}, z, \tau) - \theta(\vec{x} + \hat{r}, z, \tau)) \quad (4) \\ & -\alpha J \int_0^\beta d\tau \sum_{\vec{x}, z} \cos(\theta(\vec{x}, z, \tau) - \theta(\vec{x}, z + 1, \tau)) + \frac{1}{2e_*^2} \\ & \int_0^\beta d\tau \sum_{\vec{x}, \vec{y}, z, z'} \dot{\theta}(\vec{x}, z, \tau) V^{-1}(|\vec{x} - \vec{y}|, z - z') \dot{\theta}(\vec{y}, z', \tau), \end{aligned}$$

with $\vec{x}$ being a discrete two-dimensional (2D) vector labeling sites of a quadratic lattice, $\dot{\theta} = \partial_\tau \theta$ and $\hat{r} = \hat{x}_1, \hat{x}_2$ a lattice unit vector. The parameter $0 < \alpha < 1$ measures the *c*-axis anisotropy. The last term describes the quantum fluctuations induced by the interactions and to be specific we will assume the Coulomb interaction $V \sim 1/\sqrt{|\vec{x} - \vec{y}|^2 + (z - z')^2}$, although our arguments will be rather general. For illustration, we will also consider the short-range repulsion $V = \delta_{\vec{x}, \vec{y}} \delta_{z, z'}$. In general, one can write the helicity modulus in the model (4) as

$$\frac{\rho}{\rho_0} = F\left(\frac{e_*^2}{\rho_0}, \frac{T}{\rho_0}, \alpha\right), \quad (5)$$

where F is a dimensionless function of its three dimensionless arguments and $\rho_0 = \rho_0(J, e_*, \alpha)$ is the helicity

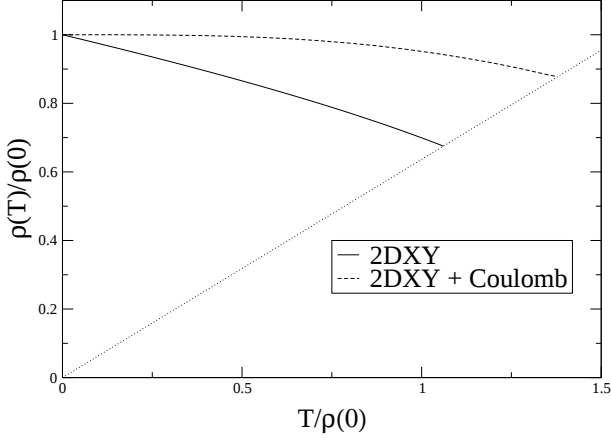


FIG. 1: Helicity modulus vs. temperature in the self-consistent Gaussian approximation, for 2D XY model ($\alpha = e_* = 0$), and with Coulomb interaction ($\alpha = 0$, $e_*^2 = 10$, and $V(\vec{q}) = 1/|\vec{q}|$). The straight dashed line denotes the universal BKT limit, $\rho(T_c) = (2/\pi)T_c$, at which the helicity modulus discontinuously vanishes. Note that T_c for fixed ρ_0 increases with interaction.

modulus at $T = 0$. (For $\alpha = e_* = 0$, for example, $\rho_0 = J$.)

Let us consider first the 2D limit, $\alpha = 0$. When $e_* = 0$ as well, the last term in (4) completely suppresses quantum fluctuations, and the Eq. (4) reduces to the standard (thermal) 2D XY model. The critical temperature for $\alpha = e_* = 0$ is given by $T_c = \rho_0/Q_{2D,XY}$, with $Q_{2D,XY} = 1.11$ [12]. The transition is in the Berezinskii-Kosterlitz-Thouless (BKT) universality class, and consequently at T_c the superfluid density has a universal discontinuity, with $\rho(T_c^-) = (2/\pi)T_c$ [13]. At low temperatures the reduction of ρ is linear in T : $\rho(T) \approx \rho_0 - T/4$ [12]. Consider now turning on a weak interaction e_* while still keeping $\alpha = 0$. This has two principal effects: 1) the reduction of ρ_0 due to quantum fluctuations [14]; 2) the introduction of a new (quantum) energy scale ω_q below which the further reduction of $\rho(T)$ with T is suppressed. In principle, increasing the interaction lifts the energies of the longitudinal (spin-wave) phase fluctuations, so $\Delta\rho(T)/\rho_0 = (\rho_0 - \rho(T))/\rho_0$ should be a decreasing function of interactions (see Fig. 1). A weak Coulomb interaction e_* , nevertheless, is an irrelevant coupling in 2D even at $T = 0$ [15] so that the finite temperature transition remains in the BKT universality class and in particular, $\rho(T_c^-) = (2/\pi)T_c$ still holds for a weak $e_* \neq 0$. Defining the dimensionless amplitude for $e_* \neq 0$ as $Q(\alpha = 0, e_*) = \rho_0/T_c$, the above discussion suggests then that

$$\frac{2}{\pi} < Q(\alpha = 0, e_*) < Q_{2D,XY}, \quad (6)$$

which we propose here as a conjecture.

The lower bound in (6) is dictated by the BKT universality class of the finite temperature transition in 2D. Our conjecture of the existence of the upper bound on Q

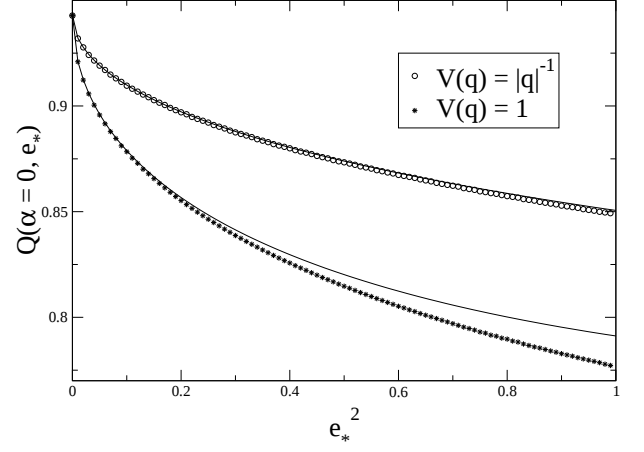


FIG. 2: The amplitude $Q(\alpha = 0, e_*) = \rho_0/T_c$ in the self-consistent Gaussian approximation for the helicity modulus in 2D, Eq. (7), with T_c defined by $\rho(T_c) = (2/\pi)T_c$, for a long-range and a short-range interactions. The lines are the weak-interaction results in Eq. (8), and $J = 1$.

in two dimensions is supported by a self-consistent calculation in which one approximates the first term in Eq. (4) (with $\alpha = 0$) by an optimally chosen Gaussian term [11]. The straightforward calculation then gives

$$-\ln \frac{\rho(T)}{J} = \frac{1}{4} \sqrt{\frac{e_*^2}{\rho(T)}} \int \frac{d^2 \vec{q}}{(2\pi)^2} F(\vec{q}) \coth \left[\frac{\sqrt{e_*^2 \rho(T)}}{T} F(\vec{q}) \right], \quad (7)$$

where $F^2(\vec{q}) = V(\vec{q}) \sum_{\hat{r}} \sin^2(\frac{\vec{q} \cdot \hat{r}}{2})$. Identifying the approximate transition temperature as the point when classical vortices unbind and the self-consistent Gaussian approximation breaks down, $\rho(T_c) = (2/\pi)T_c$, at weak interaction Eq. (7) yields

$$Q(\alpha = 0, e_*) = \frac{2e_*^{\frac{\pi}{8}}}{\pi} \left[1 - \frac{e_*}{4J^{\frac{1}{2}}} \int \frac{d^2 \vec{q}}{(2\pi)^2} F(\vec{q}) + \frac{e_*^2 e_*^{\frac{\pi}{8}}}{6\pi J} \int \frac{d^2 \vec{q}}{(2\pi)^2} F^2(\vec{q}) + O(e_*^3) \right]. \quad (8)$$

Numerical results for $Q(\alpha = 0, e_*)$ in our self-consistent Gaussian approximation are shown in Fig. 2. In both the Coulomb and the short-range case we find Q to be a decreasing function of interaction. Although the above calculation in principle includes only the longitudinal (spin-wave) phase fluctuations, it should be a reasonable indicator of the interaction dependence of the amplitude Q . Recall that the main contribution to $\Delta\rho(T)$ at temperatures $T \leq 0.8T_c$ in the classical 2D XY model actually comes from the spin-waves [16], and it is the increase of their energies with interaction that should ultimately be responsible for the proposed behavior of $Q(\alpha = 0, e_*)$.

At low temperatures $T \ll \omega_q$, from Eq. (7) one also finds that for Coulomb interactions in 2D

$$\frac{\rho(T)}{\rho_0} = 1 - \text{const.} \left(\frac{T}{\omega_q} \right)^5, \quad (9)$$

where $\omega_q = c_*^{4/5} \rho_0^{3/5}$ is the characteristic temperature scale for quantum fluctuations. For a short-range interaction one similarly finds $1 - (\rho(T)/\rho_0) \sim (T/\omega_q)^3$ in 2D, with $\omega_q = e_*^{2/3} \rho_0^{2/3}$. Both expressions show the anticipated reduction of $\Delta\rho(T)/\rho_0$ with interactions for fixed ρ_0 . Also, note that when $\rho_0 \rightarrow 0$, $\omega_q \gg \rho_0$ in general in 2D. This will have important consequences for the form of $\rho(T)$, as we will discuss shortly.

The lesson from the above considerations is that interactions are expected to *reduce* the amplitude Q from its value in the 2D XY model. Introducing the third dimension by turning on $\alpha > 0$ in (4) does the same. This is evident in the Monte Carlo results [17] as well as from the 3D value $Q_{3D,XY} = 0.45$ [18], for example. The reason behind this trend is quite physical: coupling the layers only strengthens the phase coherence so that a higher temperature is required to destroy it. Both the interactions and the coupling between the layers should decrease Q and we expect that

$$Q(\alpha, e_*) \leq Q_{2D,XY} = 1.11 \quad (10)$$

for the family of quantum XY models defined by Eq. (4). Introducing longer-ranged couplings than just between the nearest neighbors [19], as long as there is no frustration in the problem [20], would also increase the tendency to order and consequently should reduce Q further. The maximum value of $Q_{2D,XY}$ then corresponds to the weakest (unfrustrated) superfluid order on the quadratic lattice [21].

The conjectured maximum value of the ratio Q in the family of quantum XY models (4) appears to be significantly below the one characterizing the standard experimental Uemura plot. To bring the two closer one needs to assume a considerably smaller ‘thickness’ d : choosing the average spacing between the adjacent layers in YBCO, $d = 6\text{\AA}$, for example, would lead to $Q > 1.09$ from experiment, and possibly falling just slightly below our upper bound. A more natural interpretation of the above discrepancy is that an additional mechanism for the reduction of superfluid density is required. Of course, one is readily available in cuprates: nodal quasiparticles.

As well known [22, 23], with the phase fluctuations neglected, at low temperatures depletion of the helicity modulus in a 2D d-wave superconductor is entirely due to low-energy quasiparticles near the four nodes of the order parameter,

$$\rho = \rho(0) - yT + O\left(\frac{T^2}{\Delta}\right). \quad (11)$$

The number $y = (2\ln(2)/\pi)z^2(v_F/v_\Delta)$, Δ is the maximum of the superconducting gap, v_F and v_Δ are the two velocities characterizing the low-energy quasiparticle dispersion, and z is the charge renormalization factor. Assuming $\Delta \gg T_c$ in underdoped cuprates makes the correction to linear dependence in Eq. (7) negligible for $T < T_c$ and we drop it hereafter.

Very underdoped cuprates are characterized by a large gap $\Delta \gg T_c$, small transition temperature T_c , and strong

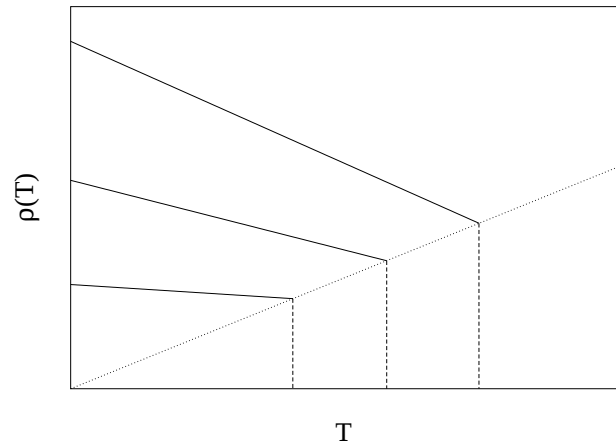


FIG. 3: Schematic behavior of the superfluid density vs. temperature in a low- T_c , large gap, quasi-2D d-wave superconductor. Doping is assumed to be decreasing from top to bottom. Note that both T_c and the slope should decrease with underdoping (see the text). Dashed line again represents the universal BKT limit.

c-axis anisotropy. We may then include both the quasiparticle and phase fluctuation contributions to the reduction of the superfluid density by reasoning as follows: 1) Assume that the $T = 0$ superconducting transition in underdoped regime is continuous. General scaling arguments imply then that *near* the quantum critical point $\rho(0) \sim T_c^{(D+z-2)/z}$, which for $D = 2$ (2D) reduces to $\rho(0) \sim T_c$ independently of the nature of the putative quantum critical point. It then follows that as $T_c \rightarrow 0$, the quantum temperature scale in Eq. (9) $\omega_q \gg T_c$ and the longitudinal phase fluctuations are strongly suppressed for *all* $T < T_c$. 2) With phase fluctuations being essentially negligible, quasiparticles alone reduce $\rho(T)$ according to Eq. (11), with only the linear term being important for $T < T_c \ll \Delta$. 3) Finally, the superfluid density in 2D still can not fall below the universal BKT value, since for $\rho(T) < (2/\pi)T$ the superfluid order would become unstable to unbinding of classical vortices. In sum, the transition temperature in a quasi-2D d-wave superconductor with $\Delta \gg T_c$ is approximately determined by

$$\rho(0) - yT_c = \frac{2T_c}{\pi}, \quad (12)$$

where $\rho(0)$ is the *physical* $T = 0$ helicity modulus, already renormalized by quantum fluctuations. $\rho(T)$ at various dopings acquires then an approximate simple form depicted schematically in Fig. 3. Virtual (bound) vortex fluctuations should additionally reduce $\rho(T)$ near T_c , and thus tend to slightly lower the transition temperature. With $0 < \alpha \ll 1$, on the other hand, some rounding of the universal BKT jump close T_c is expected, as well as a slight increase of T_c . These fine effects are being omitted from Fig. 3 for simplicity but should be expected in experiments.

The addition of the quasiparticle contribution y in Eq. (12) makes the agreement with old Uemura data imme-

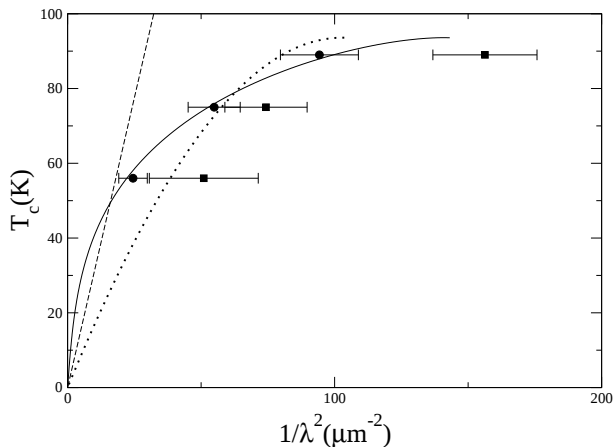


FIG. 4: Data reported in [3]. The lines are fits to the data as discussed in the text. The convexity of the curves is due to the doping dependence of the quantity $z^2(v_F/v_\Delta)$.

diately better: taking $y \approx 1$ near optimal doping [24] brings the sum in $Q = y + (2/\pi)$ closer to two. More importantly, Eq. (12) implies a systematic deviation of $T_c(\rho(0))$ from the simple linear relation due to the anticipated decrease of the slope y with underdoping. Even if one assumes the charge renormalization factor z to approximately stay constant with doping, the decrease of v_Δ [1] together with the approximate constancy of v_F [25] makes the slope y inevitably an increasing function of doping, and therefore of $\rho(0)$. The slope of the $T_c(\rho(0))$ curve should therefore be a decreasing function of $\rho(0)$, i. e. the curve should be *convex* upward. In fact we expect that the dependence of y on doping should be stronger than what would follow from the observed increase of v_Δ alone. This would be in agreement with the general theory of the fluctuating d-wave superconductors [26] and the gauge theory of t-J model [23], which both predict the charge renormalization factor $z \propto T_c$ at small dopings.

Figure 4 shows the data taken from Pereg-Barnea *et al.* [3] where circles (squares) are from $a(b)$ -axis measurements. To avoid contributions arising from chains in

the b -direction, we consider only the a -direction, though both data sets clearly show a departure from linear behavior. In fitting the data we used a straight line fit to the doping dependence of the superconducting gap Δ_0 from Sutherland *et al.* (their Figure 6) [1] and converted to v_Δ using $\Delta_0 = \hbar k_F v_\Delta / 2$ with $k_F \approx 0.7 \text{ \AA}^{-1}$. We have taken $v_F = 2.5 \times 10^7 \text{ cm/s}$. The dotted line represents then the Eq. 12 with $d = 10 \text{ \AA}$ and $z = 1$ and no fitting parameters. A somewhat better agreement is obtained by assuming $z = T_c/C$ with $C = 79 \text{ K}$, which we show as the full line, as an illustration. The reader is cautioned, however, that such a strong dependence of the slope y on T_c has not yet been directly observed. The dashed line is the linear Uemura relation with $Q = 2$, demonstrating that the data departs significantly from this behavior.

The curvature in the $T_c(\rho(0))$ plot was also noted and discussed in a recent paper by Tallon *et al.* [9] where it was attributed to the opening of an additional gap in the density of states *competing* with superconductivity. Our explanation is fundamentally different in nature and in particular, the curvature is argued to be a generic feature of two-dimensional d-wave superconductor with the increasing gap and the decreasing T_c . The microscopic mechanism behind the latter two properties of underdoped cuprates is left unaddressed here and will be a subject of a separate publication [27].

In sum, we discussed the reduction of superfluid density in a quasi-2D d-wave superconductors with low T_c and large superconducting gap. We argued that the Coulomb interaction under these conditions essentially eliminates the longitudinal phase fluctuations but that the transition at T_c should still be governed by the universal vortex physics and fall into the BKT universality class. A relation between $\rho(0)$ and T_c which takes into account both the quasiparticle contribution and the universal vortex fluctuations near T_c is proposed to explain the deviation from the linear Uemura scaling observed in recent experiments on underdoped YBCO.

We thank D. Bonn, I. Božović, D. Broun, and P. Turner for useful discussions. This work was supported by the NSERC of Canada and the Research Corporation.

-
- [1] M. Sutherland, D. G. Hawthorn, R. W. Hill, F. Ronning, S. Wakimoto, H. Zhang, C. Proust, E. Boaknin, C. Lupien, L. Taillefer, R. Liang, D. A. Bonn, W. N. Hardy, R. Gagnon, N. E. Hussey, T. Kimura, M. Nohara, and H. Takagi, *Phys. Rev. B*, **67**, 174520 (2003).
 - [2] Y. J. Uemura, G. M. Luke, B. J. Sternlieb, J. H. Brewer, J. F. Carolan, W. N. Hardy, R. Kadono, J. R. Kempton, R. F. Keiff, S. R. Kretzman, P. Mulhern, T. M. Riseman, D. L. Williams, B. X. Yang, S. Uchida, H. Takagi, J. Gopalakrishnan, A. W. Sleight, M. A. Subramanian, C. L. Chien, M. Z. Cieplak, G. Xiao, V. Y. Lee, B. W. Statt, C. E. Stronach, W. J. Kossler, and X. H. Yu, *Phys. Rev. Lett.* **62**, 2317 (1989).
 - [3] T. Pereg-Barnea, P. J. Turner, R. Harris, G. K. Mullins, J. S. Bobowski, M. Raudsepp, R. Liang, D. A. Bonn, and W. N. Hardy, *Phys. Rev. B* **69**, 184513 (2004).
 - [4] J. W. Guikema, J. H. Bluhm, D. A. Bonn, R. Liang, W. N. Hardy, and K. A. Moler, preprint, unpublished.
 - [5] For older measurements showing a similar trend, see for example, C. L. Seaman, J. J. Neumeier, M. B. Maple, L. P. Le, G. M. Luke, B. J. Sternlieb, Y. J. Uemura, J. H. Brewer, R. Kadono, R. F. Kiefl, S. R. Kretzman, and T. M. Riseman, *Phys. Rev. B* **42**, 6801 (1990).
 - [6] T. Schneider and J. M. Singer, *Phase Transition Approach to High Temperature Superconductivity*, (Imperial College Press, 2000), Ch. 7.

- [7] I. Božović, J. N. Eckstein, M. E. Klausmeierbrown, and G. Virshup, *J. Supercon.* **5**, 19 (1992).
- [8] R. G. Goodrich, P. W. Adams, D. H. Lowndes, and D. P. Norton, *Phys. Rev. B* **56**, R14299 (1997).
- [9] J. L. Tallon, J. W. Loram, J. R. Cooper, C. Panagopoulos, and C. Bernhard, *Phys. Rev. B*, **68**, 180501(R) (2003).
- [10] V. J. Emery and S. A. Kivelson, *Nature (London)* **374**, 434 (1995).
- [11] E. Roddick and D. Stroud, *Phys. Rev. Lett.* **74**, 1430 (1995).
- [12] R. Gupta, J. DeLapp, G. G. Batrouni, G. C. Fox, C. F. Baillie, and J. Apostolakis, *Phys. Rev. Lett.* **61**, 1996 (1988); R. Gupta and C. F. Baillie, *Phys. Rev. B* **45**, 2883 (1992).
- [13] D. R. Nelson and J. M. Kosterlitz, *Phys. Rev. Lett.* **39**, 1201 (1977).
- [14] S. Doniach and M. Inui, *Phys. Rev. B* **41**, 6668 (1990).
- [15] I. F. Herbut, *Phys. Rev. Lett.* **87**, 137004 (2001).
- [16] P. Minnhagen, *Rev. Mod. Phys.* **59**, 1001 (1987).
- [17] E. W. Carlson, S. A. Kivelson, V. J. Emery, and E. Manousakis, *Phys. Rev. Lett.* **83**, 612 (1999).
- [18] J. Adler, C. Holm, and W. Janke, *Physica A* **201**, 581 (1993).
- [19] W. Kim and J. P. Carbotte, cond-mat/0309261.
- [20] We are assuming that the additional terms $\sim J_n \cos(n(\theta(\vec{x}, z) - \theta(\vec{y}, z')))$ with $n \geq 2$ in Eq. (4), which effectively introduce such frustration (see ref. 17), are negligible.
- [21] We did not include the ‘Berry phase’ term $in_0 \int d\tau \sum_{\vec{x}, z} \dot{\theta}(\vec{x}, z, \tau)$ in Eq. (4). At low temperatures such term vanishes for the spin-wave phase fluctuations, and it is also irrelevant at the BKT transition at T_c . We therefore do not expect it to affect our arguments leading to the inequality (10).
- [22] H. Won and K. Maki, *Phys. Rev. B*, **49**, 1397 (1994).
- [23] P. A. Lee and X.-G. Wen, *Phys. Rev. Lett.* **78**, 4111 (1997).
- [24] D. A. Bonn, S. Kamal, A. Bonakdarpour, R. Liang, W. N. Hardy, C. C. Homes, D. N. Basov, and T. Timusk, *Czech. J. Phys.* **46**, 3195 (1996).
- [25] A. Damascelli, Z. Hussain, and Z-X. Shen, *Rev. Mod. Phys.* **75**, 473 (2003).
- [26] I. F. Herbut, *Phys. Rev. Lett.* **88**, 047006 (2002); *Phys. Rev. B* **66**, 094504 (2002); preprint cond-mat/0302058.
- [27] I. F. Herbut, preprint, cond-mat/0403095.